

AD-A188 345

SPECTROSCOPIC CHARACTERIZATION OF TITANIUM DOPED  
SAPPHIRE(U) HEBREW UNIV JERUSALEM (ISRAEL) DEPT OF  
INORGANIC AND ANALYTICAL CHEMISTRY R REISFELD  
38 SEP 87 DAJA45-85-M-8344


1/1

UNCLASSIFIED

F/G 11/6

NL



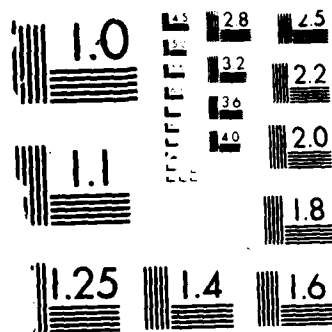

U.S. GOVERNMENT PRINTING OFFICE: 1963

DTIC FILE COPY

1

SPECTROSCOPIC CHARACTERIZATION OF TITANIUM DOPED SAPPHIRE

AD-A180 345

Final Report

DTIC  
ELECTE  
MAY 15 1987  
S D

submitted by

Professor Renata Reisfeld  
Department of Inorganic and Analytical Chemistry  
The Hebrew University of Jerusalem  
Jerusalem 91904 Israel

to

US Army  
Contract No. DAJA 45-85-M-0344

1 October 1985 - 30 September 1987

**DISTRIBUTION STATEMENT A**  
Approved for public release  
Distribution Unlimited

## REPORT DOCUMENT

AD-A180 345

Form Approved  
OMB No 0704-0188  
Exp Date Jun 30, 19861a REPORT SECURITY CLASSIFICATION  
UNCLASSIFIED2a SECURITY CLASSIFICATION AUTHORITY  
USARDSG-UK2b DECLASSIFICATION/DOWNGRADING SCHEDULE  
NOT APPLICABLE

4. PERFORMING ORGANIZATION REPORT NUMBER(S)

6a. NAME OF PERFORMING ORGANIZATION  
THE HEBREW UNIVERSITY OF JERUSALEM6b. OFFICE SYMBOL  
(if applicable)

3. DISTRIBUTION/AVAILABILITY OF REPORT

APPROVED FOR PUBLIC RELEASE;  
DISTRIBUTION UNLIMITED5. MONITORING ORGANIZATION REPORT NUMBER(S)  
R&D 4697-MS-01 FINAL REPORT7a. NAME OF MONITORING ORGANIZATION  
USARDSG-UK6c. ADDRESS (City, State, and ZIP Code)  
DEPT. OF INORGANIC CHEMISTRY  
JERUSALEM 91904  
ISRAEL7b. ADDRESS (City, State, and ZIP Code)  
P.O. BOX 65  
FPO NEW YORK, 09510-15008a. NAME OF FUNDING/SPONSORING  
ORGANIZATION  
EUROPEAN RESEARCH OFFICE8b. OFFICE SYMBOL  
(if applicable)  
USARDSG-UK9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER  
CONTRACT # DAJA 45-85-M-03448c. ADDRESS (City, State, and ZIP Code)  
223 OLD MARYLEBONE RD.  
LONDON NW1 5TH, U.K.

10. SOURCE OF FUNDING NUMBERS

PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT ACCESSION NO.
61102A	1L	61102BH57-02	

11. TITLE (Include Security Classification)

(U) "SPECTROSCOPIC CHARACTERIZATION OF TITANIUM DOPED SAPPHIRE"

12. PERSONAL AUTHOR(S)  
PROFESSOR RENANTA REISFELD13a. TYPE OF REPORT  
FINAL13b. TIME COVERED  
FROM \_\_\_\_\_ TO \_\_\_\_\_

14. DATE OF REPORT (Year, Month, Day)

15. PAGE COUNT

16. SUPPLEMENTARY NOTATION

NONE

COSATI CODES		
FIELD	GROUP	SUB-GROUP

18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)

Titanium, Iron

19. ABSTRACT (Continue on reverse if necessary and identify by block number)

Abstract: Titanium(III) in corundum shows a short-lived (3.1  $\mu$ s) broad  $^2E - ^2T_2$  luminescence around 740 nm, and a 10 times longer-lived  $^2A_1(^4s) - ^2T_2$  centered around 410 nm. Both these broad-band emissions with large Stokes shift show prospects for tunable lasers. The absorption spectrum is studied in detail, and traces of titanium(IV) are shown not to be involved in the "violet" emission, in contrast to a parasitic absorption around 700 nm due to Ti(III,IV), like sapphire is blue due to Fe(II)Ti(IV)  $\rightarrow$  Fe(III)Ti(III) electron transfer bands.

20. DISTRIBUTION/AVAILABILITY OF ABSTRACT

☒ UNCLASSIFIED/UNLIMITED ☒ SAME AS RPT ☒ DTIC USERS

21. ABSTRACT SECURITY CLASSIFICATION

UNCLASSIFIED

22a. NAME OF RESPONSIBLE INDIVIDUAL

DR. IOBAL AHMAD, CHIEF, MATERIALS SCIENCE BR

22b. TELEPHONE (Include Area Code)

409-4423

AMXSN-IJK-TM

22c. OFFICE SYMBOL

The original proposal was scheduled for 1 Oct.1985 to 30 Sept.1986. However, since the crystals were obtained only in May 1986, an extension for the work was granted for an additional year.

The doped sapphire crystals were kindly supplied by Dr. R.N. Katz and Dr. J.L. Caslavsky of the Ceramics Research Division, Army Materials and Mechanics Research Center, Watertown, Massachusetts 02172, USA.

The report consists of the paper which was sent to Chimia:

Unusual Luminescence of Titanium(III) in Aluminium Oxide,  
R.Reisfeld, M. Eyal and C.K. Jørgensen.



Accession For	
NTIS CRA&I	<input checked="checked" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

# Unusual Luminescence of Titanium(III) in Aluminium Oxide

Renata Reisfeld, Marek Eyal and Christian K. Jørgensen \*

**Abstract:** Titanium(III) in corundum shows a short-lived ( $3.1 \mu\text{s}$ ) broad  $^2\text{E} - ^2\text{T}_2$  luminescence around 740 nm, and a 10 times longer-lived  $^2\text{A}_1$  ("4s")- $^2\text{T}_2$  centered around 410 nm. Both these broad-band emissions with large Stokes shift show prospects for tunable lasers. The absorption spectrum is studied in detail, and traces of titanium(IV) are shown not to be involved in the "violet" emission, in contrast to a parasitic absorption around 700 nm due to Ti(III,IV), like sapphire is blue due to Fe(II)Ti(IV)  $\rightarrow$  Fe(III)Ti(III) electron transfer bands.

\* Correspondence: Prof. Dr. h.c. C. K. Jørgensen

Département de Chimie minérale, analytique et appliquée

Université de Genève

Quai Ernest Ansermet 30, CH-1211 Geneva 4

Prof. Dr. R. Reisfeld, Dr. M. Eyal

Department of Inorganic Chemistry

Hebrew University

91904 Jerusalem (Israel)

\*\* Acknowledgements: We are very grateful to Dr. Jaroslav L. Caslavsky and Dr. Robert N. Katz, Ceramics Research Division, U.S. Army Materials Technology Laboratory, Watertown, Massachusetts 02172, for the highly valuable crystalline samples studied here. This work was supported in part by the U.S. Army European Research Office (London) under contract DAJA 45-85-M-0344. The grant no. 2.820-0.85 from the Swiss National Science Foundation made the collaboration possible between the universities in Jerusalem and Geneva.

Corundum, the  $\alpha$ -modification of  $\text{Al}_2\text{O}_3$ , has almost exactly regular octahedral sites for the cation, though spectroscopic characteristics in polarized light clearly indicate the uniaxial hexagonal crystal type. Those trivalent ions which form hydrated alums can be incorporated on the octahedral site, and for instance,  $\text{Al}_2\text{O}_3$ ,  $\text{Cr}_2\text{O}_3$  and  $\text{Fe}_2\text{O}_3$  are fully miscible. The absorption spectra of trivalent 3d group ions in corundum were studied [1] when the first laser, the ruby  $\text{Cr}_x\text{Al}_{2-x}\text{O}_3$  with  $x \sim 0.01$ , was operated in 1960. Though the colourless corundum (nearly as hard as diamond, and used in optical components transparent in the far ultraviolet) frequently is called sapphire, this blue mineral contains simultaneously small amounts of iron(II) and titanium(IV) on the octahedral sites, and the broad absorption band [2,3] at 575 nm with a shoulder at 720 nm is due to electron transfer forming, to the first approximation,  $3d^5$  iron(III) and  $3d^1$  titanium(III) in the excited state, as frequently found [4-6] in compounds containing iron(II) at short distances from oxidizing ions, including iron(III). The black mineral ilmenite  $\text{FeTiO}_3$  has an ordered super-structure of corundum. It may be noted that ilmenite-type  $\text{Ni}_x\text{Mg}_{1-x}\text{TiO}_3$  and  $\text{Ni}_x\text{Cd}_{1-x}\text{TiO}_3$  were studied by Reinen, allowing important conclusions [7] about the  $3d^8$  states of nickel(II) corresponding to the absorption bands.

Some lasers, based on gaseous atoms or positive ions, emit spectral lines. This is almost true also for rare earths containing a partly filled 4f shell [8,9]. On the other hand, fluorescent organic colorants in solution, or excimer lasers based on ephemeric diatomic molecules in gases, emit broad luminescence bands, and under favourable conditions, can be used for tunable lasers, such as certain cases of  $3d^3$  chromium(III) emitting a broad band in the near infrared from the first excited quartet state  $^4T_2$  to the groundstate  $^4A_2$ . Since  $^4T_2$  has one strongly anti-bonding d-like electron, the Franck-Condon principle demands the co-excitation of a broad vibronic continuum belonging to the groundstate. The situation is quite different in the narrow-band emission of ruby, where the first doublet state  $^2E$  involves the same three roughly non-bonding electrons as  $^4A_2$ . Tunable lasers emitting from  $^4T_2$  in the isoelectronic vanadium(II) incorporated in rutile-type  $\text{V}_x\text{Mg}_{1-x}\text{F}_2$  have been studied [10] but present difficulties of black-out due to colour centres formed during large-scale operation.

Titanium(III) has one 3d electron which can be excited (by light close to 500 nm) to the two anti-bonding orbitals with angular functions proportional to  $(x^2-y^2)$  and  $(3z^2-r^2)$ . If the octahedron  $TiX_6$  was exactly regular, these two orbitals would have identical energies. Actually, the hexa-aqua ion in acidic, non-complexing solutions [11,12] shows a shoulder at 575 nm on the asymmetric peak at 492 nm. This can hardly be ascribed to a distorted environment, as would be conceivable in a doped crystal (especially in the case of quite differing ionic radii). It may be relevant that the isoelectronic vanadium(IV) forms the highly anisotropic [12,13] blue vanadyl aqua ion  $VO(OH_2)_4^{+2}$  containing its unpaired electron in the orbital  $(xy)$  which is the only non-bonding 3d orbital in the case of strong  $\pi$ -anti-bonding effects of oxo ligands on the z Cartesian axis. The diamagnetic groundstate of  $MO_2X_4$  complexes [14] of M=ruthenium(VI); rhenium(V) and osmium(VI) corresponds to two electrons in  $(xy)$ . It is generally argued that the splitting of the visible absorption band of titanium(III) is due to the Jahn-Teller effect. The slightly problematic side of this explanation is that Jahn-Teller-stable groundstates do not provide band splittings by transitions to even highly separated potential surfaces in the 16-dimensional space corresponding to 7 nuclei in  $MX_6$  [13]. However, a quite weak deviation from  $O_h$  in the groundstate can produce strong energy separations by Franck-Condon projection on high-lying potential surfaces, much in the same way as the width of "ligand field" absorption bands, though originating in the thermal (and zero-point) vibration [15], frequently is 10 times  $kT$ , and largest for the lightest ligands. In the octahedral d-group complexes, the typical cases of strong Jahn-Teller splitting occur for unbalanced occupation of  $(x^2-y^2)$  and  $(3z^2-r^2)$  in the groundstate, actually by 0 and 1 electron in the quintet groundstates of  $3d^4$  chromium(II) and manganese(III); and by 1 and 2 electrons in  $3d^9$  copper(II). A few instances are known [16] of pronounced band splitting of iron(II) hexa-aqua ions and in the quintet groundstate hexafluoro complex of cobalt(III). Since the two  $\sigma$ -anti-bonding orbitals have each one electron, the phenomenon is here ascribed to Jahn-Teller effect in the (at most)  $\pi$ -anti-bonding  $(xy)$ ,  $(xz)$  and  $(yz)$  accommodating 4 electrons. It is known from chromium(III) complexes [17] that  $\pi$ -anti-bonding effects are up to 30 percent of the  $\sigma$ -anti-bonding effect, the highest ratio is observed for fluoride ligands. Hence, it can be concluded that the weak Jahn-Teller effect on titanium(III) is induced by the  $\pi$ -anti-bonding only. Because of the mechanism of the Stokes shift, the consequences are likely to be more pronounced for luminescence than for



absorption. Jahn-Teller effects for the excited  ${}^4T_2$  of chromium(III) in cubic crystals have been detected [18] in the vibrational fine-structure (below 10 K) of the broad emission band.

Powell et al. [3] recently studied the absorption and emission spectra of  $Ti_xAl_{2-x}O_3$  and found an asymmetric band (we find the maximum at 483 nm and a shoulder at 550 nm) surprisingly similar to the aqua ion in alums [11] and in acidic solutions. The near-infrared emission occurs in a broad band around 740 nm, satisfying one of the necessary conditions for tunable lasers [10]. This emission in corundum has been studied by two other groups [19-21] and one of the difficulties for obtaining a positive amplification along the laser path is a somewhat unpredictable absorption between 700 and 850 nm. Though it is difficult to study trace impurities in crystals almost as hard as diamond, it does not seem to be Fe(II), Ti(IV) providing the blue colour of sapphire [3] but rather adjacent Ti(III,IV) sites known [12] in 12 molar hydrochloric acid, where simultaneously present (very pale yellow) Ti(IV) and a sky-blue Ti(III) chloro complex (with maximum at 525 nm) form a dark brownish-purple 1:1 complex with a 8 times stronger, broad band at 482 nm, having a shoulder at 670 nm. The formation constant of this complex is  $12\text{ M}^{-1}$  showing a pronounced affinity between the two (chloro-bridged) oxidation states. The diagnosis is that parasitic absorption can be avoided in titanium(III) doped corundum if all traces of Ti(IV) can be reduced to Ti(III), or at least kept at large average distance from the Ti(III) providing the main absorption.

As described in the experimental section, we studied three crystalline samples, among which one (R 10) does not present the flat background absorption slightly decreasing from 650 to 850 nm, as do the samples R 4 and R 8. In all three samples, excitation at 488 nm, monitoring emission at 732 nm, and also in R 10 excited at 488 nm and monitored at 650 and 850 nm, the decay curve (after an initial rise-time of  $3 \cdot 10^{-7}$  s suggesting rapid energy transfer from states producing much stronger ultraviolet absorption than the "4s" state discussed below) is almost exactly exponential with the life-time  $(3.1 \pm 0.1)\text{ }\mu\text{s}$ . This is comparatively short, since the radiative life-time

$$\tau_{\text{rad}} = (e_2/e_1) 2.3 \cdot 10^{-8} \text{ s} / [P(h\nu/\text{eV})^2] \quad (1)$$

is close to  $3 \cdot 10^{-5}$  s for the Ti(III) aqua ion [15] having the oscillator strength  $P = 1.2 \cdot 10^{-4}$  if the debatable ratio between  $e_2$  excited states and  $e_1$  states in the ground level is put equal to 1. As seen in the

experimental section, the  $\epsilon$  values at 488 nm for Ti(III) in corundum are closely similar to 4.1 for the aqua ion in solution, as well as the shape of the absorption band. Hence, it seems that the order of magnitude for the quantum yield of near-infrared luminescence is close to 0.1.

A much more spectacular luminescence of all three samples is a broad emission band (Figure 1) having the maximum at 410 nm and half the peak intensity at 365 and 460 nm. This "violet" emission was already reported by Powell et al. [3] at 420 nm with observed life-time  $\tau = 2.3 \mu\text{s}$ . As seen in Table 1, we find life-times gliding from 15 toward 35  $\mu\text{s}$  for most of the emission wave-lengths studied, for excitation of all three samples at 337 nm. On the other hand, we did not find any dependence on the exciting wave-length of the position and shape of the emission band. The luminescence may very well be due to a superposition of two or several mechanisms, the slowest corresponding to the asymptotic value of  $\tau$  close to 30 microseconds.

Searching the emitting state, we measured the excitation spectra for emission at 350, 400 and 450 nm, and found in all three samples an (energy-wise) quite broad band at 265 nm. One may feel some doubts whether superposed competing absorption bands shift this excitation maximum at 265 nm from the average position of the emitting state. Going from the absorption maximum toward ultraviolet, the minimum  $\epsilon \sim 2$  occurs at 405 nm, and  $\epsilon = 5$  is crossed close to 310 nm. The subsequent increase is very smooth, and reaches  $\epsilon = 200$  close to 245 nm. There are no evident shoulders between 300 and 250 nm, and  $\epsilon \sim 25$  at 265 nm.

Since mixed oxides containing titanium(IV) absorb very strongly in the near ultraviolet, in contrast to the much less oxidizing zirconium(IV) and thorium(IV), one might expect an electron transfer state of Ti(IV) producing the "violet" emission in analogy to solid vanadates [22]. This is rendered unlikely by the essentially similar absorption spectra in the ultraviolet, and the emission characteristics, of R 4 and R 8 compared with the sample R 10 lacking near-infrared absorption indicating absence of admixed Ti(IV). Hence, the "violet" emission seems to originate in Ti(III).

The most attractive hypothesis is a transition of the single 3d electron to a 4s-like orbital. Such a transition may be very weak, and if the asymptotic  $\tau \sim 30 \mu\text{s}$  is not an artifact of energy trapping [23], equation (1) provides  $\tau_{\text{rad}} \sim \tau$  for  $P = (e_2/e_1) \cdot 4 \cdot 10^{-5}$ . Since the quantum yield  $\eta$  cannot be above 1, this is a higher limit for  $P$  (which is to be multiplied by  $\eta$  if below 1). This means that the absorption corresponding

to "violet" emission is a few times weaker than the band at 483 nm, and one can hardly hope a contribution to  $\epsilon$  below 2 to be detectable below 300 nm.

3d - "4s" transitions have only been detected in compounds of a few reducing d-group ions. The best characterized case [15] is the band of  $\text{Fe}(\text{OH}_2)_6^{+2}$  at 248 nm ( $40300 \text{ cm}^{-1}$ ) having  $\epsilon=18$  and  $P=3.5 \cdot 10^{-4}$ . The position may be compared with the two levels of  $3d^5 4s$  of gaseous  $\text{Fe}^{+2}$ ,  $^7S_3$  situated  $30089 \text{ cm}^{-1}$  and  $^5S_2$  at  $40999 \text{ cm}^{-1}$  above the  $3d^6$  groundstate. Two counter-acting influences modify the 3d-4s separation: the effective positive charge is smaller [7-9] in the compound; but the 4s orbital is always anti-bonding with respect to any set of ligating atoms, as can be seen from gaseous  $\text{Cu}^+$  of which the levels  $^3D_3$  (21929),  $^3D_2$  (22847),  $^3D_1$  (23998) and  $^1D_2$  (26264) of  $3d^9 4s$  are situated the number of  $\text{cm}^{-1}$  (given in parenthesis) above the closed-shell groundstate. These levels may be compared with a band [24] of the newly detected complex  $\text{Cu}(\text{NH}_3)_3^+$  at 290 nm ( $34000 \text{ cm}^{-1}$ ) having  $\epsilon \sim 300$ , whereas  $\text{Cu}(\text{NH}_3)_2^+$  absorbs less and begins at higher energy. The strong dependence of intensities of parity-forbidden transitions on the local symmetry is well-known from internal transitions in the partly filled 3d shell, e.g. of octahedral and tetrahedral cobalt(II) complexes. The 3d-"4s" transitions start at  $31500 \text{ cm}^{-1}$  in  $\text{Cu}_x\text{Na}_{1-x}\text{F}$  and are quite weak [25].

Besides corundum, there are very few cases known of titanium(III) luminescence. Recently [26], a fluorophosphate glass was studied in Shanghai. The absorption increases strongly below 350 nm and shows a peak at 529 nm and a shoulder at 685 nm. Excitation at 308 nm produces a very broad emission centered around 530 nm with  $\tau$  of order  $10 \mu\text{s}$  at 77 K, but depending to some extent on the emission wave-length, as one might expect from differing sites in the glass [9,23]. It is likely that this green emission with an enormous Stokes shift (from a maximum in the excitation spectrum at 290 nm) is analogous to the "violet" emission studied here.

### Experimental

The crystals obtained by the VSOM technique previously described [3] were polished with two parallel surfaces typically separated by 1 cm.

The samples selected were:

R 4: density  $d=3.795 \text{ g/cm}^3$ , nominal titanium concentration  $c_{\text{Ti}} = 0.01425 \text{ mole/L}$ .

R 8:  $d=3.744 \text{ g/cm}^3$  and  $c_{\text{Ti}} = 0.01425 \text{ mole/L}$ .

P 10:  $d=3.928 \text{ g/cm}^3$  and  $c_{\text{Ti}} = 0.01475 \text{ mole/L}$ .

## Steady-state measurements:

Absorption spectra were measured of the crystal against air on a Perkin-Elmer double-beam spectrophotometer model Lambda 3. Assuming the  $c_{Ti}$  given above, the molar extinction coefficient  $\epsilon$  at 488 nm was found to be 4.5 for R 4; 4.9 for R 8; and 3.9 for R 10.

Emission and excitation spectra were measured with the Perkin-Elmer L3 with a B&L home-made, and a Spex home-made, spectrofluorimeter. Excitation at 265 nm was performed with radiation from a high-pressure xenon lamp gone through a monochromator.

## Life-time measurements:


A nitrogen laser (337 nm) was used directly for exciting "violet" emission, and combined with the dye no.8 emitting at 488 nm for exciting the red and near-infrared emission. Table 1 gives the folded life-time  $\tau_1$  (for  $e^{-1}$  times the original intensity),  $\tau_2$  (half the time for  $e^{-2}$ ) and  $\tau_3$  (a-third the time for  $e^{-3}$ ), all in microseconds, of the emission studied at wave-lengths between 350 and 732 nm of the three samples.

Table 1. Life-times in microseconds of "violet" emission of titanium(III) in corundum excited at 337 nm, and emission measured at the nm value given.  $\tau_n$  are defined in the experimental section.

Sample	nm	$\tau_1$	$\tau_2$	$\tau_3$
R 4	350	1.8	6.3	10.3
R 4	400	3.1	12.6	19.4
R 4	450	11.7	18.9	24.2
R 4	500	24.1	28.4	29.2
R 4	542	18.8	31.3	30.3
R 4	600	23.7	32.5	29.4
R 4	650	15.2	29.8	30.8
R 4	732	4.2	17.1	28.2
R 8	542	23.1	32.6	29.4
R 10	542	15.7	30.5	34.8

Fig.1. Emission spectrum (full line; excited in an interval around 265 nm) and excitation spectrum (dashed line; emission measured at 450 nm) of sample R 4.

Fig.1. Emission spectrum (full line; excited in an interval around 265 nm) and excitation spectrum (dashed line; emission measured at 450 nm) of sample R 4.

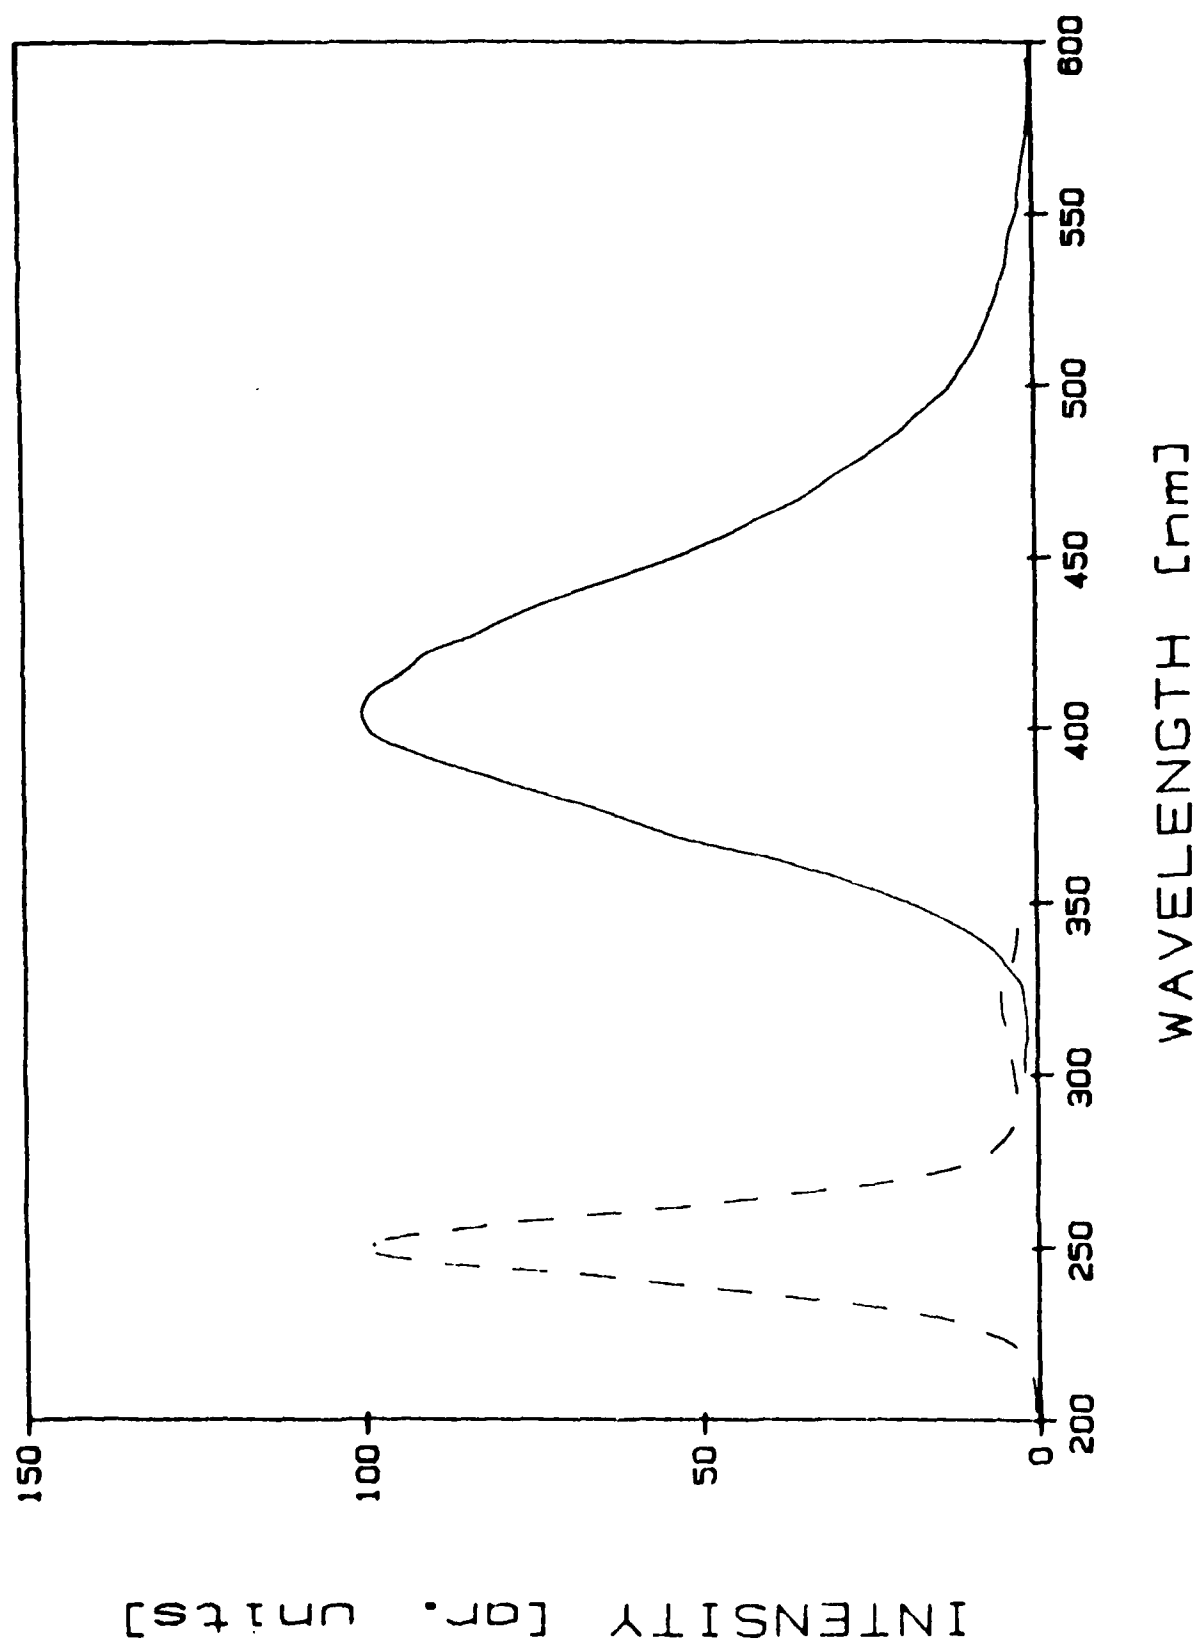

- [1] D.S. McClure, J. Chem. Phys. 36 (1962) 2757.
- [2] K. Nassau, Am. Mineral. J. 63 (1978) 219.
- [3] R.C. Powell, J.L. Caslavsky, Z. AlShaiieb, J.M. Bowen,  
J. Appl. Phys. 58 (1985) 2331.
- [4] M.B. Robin, P. Day, Adv. Inorg. Chem. Radiochem. 10 (1967) 247.
- [5] C.K. Jørgensen, Progress Inorg. Chem. 12 (1970) 101.
- [6] G.C. Allen, M.B. Wood, J.M. Dyke, J. Inorg. Nucl. Chem. 35 (1973) 2311.
- [7] C.K. Jørgensen: Oxidation Numbers and Oxidation States,  
Springer, Berlin (1969).
- [8] R. Reisfeld, C.K. Jørgensen: Lasers and Excited States of Rare  
Earths, Springer, Berlin (1977).
- [9] R. Reisfeld, C.K. Jørgensen, in K. Gschneidner, LeRoy Eyring (Ed.):  
Handbook on the Physics and Chemistry of Rare Earths, Vol. 9,  
North-Holland, Amsterdam (1987).
- [10] P. Hammerling, A.B. Budgor, A. Pinto (Ed.): Tunable Solid State Lasers,  
Springer series in Optical Sciences 47, Springer, Berlin (1985).
- [11] H. Hartmann, H.L. Schläfer, Z. Naturforsch. 6 a (1951) 760.
- [12] C.K. Jørgensen, Acta Chem. Scand. 11 (1957) 73.
- [13] C.K. Jørgensen, Topics Current Chem. 124 (1984) 1.
- [14] C.K. Jørgensen, Rev. Chim. Minér. 14 (1977) 127.
- [15] C.K. Jørgensen, Adv. Chem. Phys. 5 (1963) 33.
- [16] F.A. Cotton, M.D. Meyers, J. Am. Chem. Soc. 82 (1960) 5023.
- [17] J. Glerup, O. Mønsted, C.E. Schäffer, Inorg. Chem. 15 (1976) 1399.
- [18] R. Knochenmuss, C. Reber, M.V. Rajasekharan, H.U. Güdel,  
J. Chem. Phys. 85 (1986) 4280.
- [19] P. Lacovara, L. Esterowitz, R. Allen, Optics Lett. 10 (1985) 23.
- [20] P. Lacovara, L. Esterowitz, M. Kotka, IEEE J. Quantum Electron.  
QE-21 (1985) 1614.
- [21] N.P. Barnes, D.K. Remelius, Digest of Technical Papers, CLEO Conference  
on Lasers and Electro-Optics, Baltimore, May 1985, p. 168.  
Optical Society of America, Washington D.C. (1985).
- [22] G. Blasse, Structure and Bonding 42 (1980) 1.
- [23] R. Reisfeld, M. Eyal, C.K. Jørgensen, A.H. Guenther, B. Bendow,  
Chimia 40 (1986) 403.
- [24] J. Bjerrum, Acta Chem. Scand. A 40 (1986) 233.
- [25] D.S. McClure, C. Pedrini, J. Lumin. 31 (1984) 197.
- [26] Liu Huimin, Gan Fuxi, J. Non-Cryst. Solids 80 (1986) 422.
- [27] J.L. Caslavsky: The Growth of Large Diameter Single Crystals by  
Vertical Solidification of the Melt, in E. Kaldis (Ed.): Crystal  
Growth of Electronic Materials, p. 113, Elsevier, Amsterdam and New  
York (1985).

END

6-87

DTIC